

LITERATURE REVIEW: STRATEGIES FOR ENHANCING THE PERFORMANCE OF $\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$ CATHODE MATERIALS FOR LI-ION BATTERIES

Yola Bertilsya Hendri¹, Heni Sugesti², Zuqni Meldha¹, Lisa Legawati¹, Salma Liska¹, Yogi Yolanda¹, Amun Amri^{1*}

¹ Department of Chemical Engineering, University of Riau, Pekanbaru 28293, Indonesia.

² Department of Chemical Engineering, Politeknik Negeri Sriwijaya, Palembang 30128, Indonesia.

*E-mail: amun.amri@eng.unri.ac.id

Article History

Received: 06 September 2025; Received in Revision: 24 September 2025; Accepted: 25 September 2025

Abstract

$\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$ layered oxides Cathode Materials are among the most widely studied cathode materials for lithium-ion batteries due to their high gravimetric and volumetric energy density compared to other type cathode materials. However, the practical deployment of Ni-rich NCM materials is hindered by severe degradation mechanisms, including cation-mixing, surface reconstruction, electrolyte reactivity, transition metal dissolution, and oxygen release, which compromise cycling stability and safety. This review systematically synthesizes recent progress in advanced modification strategies designed to mitigate degradation in $\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$ cathodes. The discussion is structured into four major approaches: (i) surface modification, which employs protective coatings to suppress interfacial reactions and stabilize the cathode-electrolyte interphase; (ii) elemental doping, which strengthens the lattice, reduces cation mixing, and inhibits oxygen evolution; (iii) single-crystal engineering, which eliminates grain-boundary failure and improves thermal stability; and (iv) concentration-gradient architectures, which alleviate internal stress and enhance the durability of Ni-rich cathodes. Empirical evidence demonstrates that these strategies not only extend cycle life but also provide mechanistic insights into the underlying degradation pathways. By consolidating findings from recent experimental, this review highlights the necessity of integrating structural, chemical, and morphological interventions to realize the full potential of Ni-rich NCM cathodes. The insights presented offer a framework for designing safer, higher-performance, and commercially scalable lithium-ion batteries.

Keywords: $\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$, Lithium-ion Battery, Surface Coating, Elemental Doping, Single-Crystal Structure, Concentration Gradient, Degradation Mechanisms

Abstrak

$\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$ berbasis oksida berlapis merupakan salah satu material katoda yang paling banyak dikaji dalam pengembangan baterai litium-ion. Keunggulan utamanya terletak pada kerapatan energi gravimetri dan volumetri yang lebih tinggi dibandingkan dengan jenis katoda lain. Namun demikian, penerapan praktis material NCM kaya nikel masih menghadapi sejumlah kendala serius akibat berbagai mekanisme degradasi, antara lain pencampuran kation, rekonstruksi permukaan, reaktivitas dengan elektrolit, pelarutan logam transisi, serta pelepasan oksigen. Mekanisme-mekanisme tersebut secara langsung menurunkan stabilitas siklus dan tingkat keselamatan baterai. Ulasan ini menyajikan sintesis sistematis mengenai perkembangan mutakhir strategi modifikasi lanjutan yang dirancang untuk menekan degradasi pada katoda $\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$. Terdapat empat pendekatan utama yang dibahas, yaitu: (i) modifikasi permukaan, melalui penerapan lapisan pelindung guna menekan reaksi antarmuka dan menstabilkan lapisan katoda-elektrolit; (ii) doping unsur, yang berfungsi memperkuat struktur kisi, mengurangi pencampuran kation, serta menekan evolusi oksigen; (iii) rekayasa kristal tunggal, yang mengatasi kegagalan pada batas butir sekaligus meningkatkan stabilitas termal; dan (iv) arsitektur gradien konsentrasi, yang mampu meredam tegangan internal dan memperpanjang daya tahan katoda kaya nikel. Hasil-hasil empiris menunjukkan bahwa penerapan strategi tersebut tidak hanya memperpanjang umur pakai siklus, tetapi juga memperkaya pemahaman tentang mekanisme degradasi yang mendasari. Dengan mengintegrasikan temuan-temuan eksperimental terbaru, ulasan ini menegaskan pentingnya perpaduan intervensi struktural, kimia, dan morfologis untuk mengoptimalkan kinerja katoda NCM kaya nikel. Wawasan yang dihadirkan sekaligus menawarkan kerangka konseptual bagi pengembangan baterai litium-ion yang lebih aman, berkapasitas tinggi, dan memiliki prospek komersialisasi yang luas.

Kata kunci: $\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$, Baterai Litium-ion, Pelapisan Permukaan, Doping Unsur,

1. Introduction

The rapid expansion of global energy demand has long been sustained by fossil fuels such as coal, oil, and natural gas (Byeon et al. 2024). While renewable energy technologies continue to grow, fossil energy sources still dominate the global energy portfolio, raising concerns about finite reserves, carbon emissions, and environmental degradation. As nations pursue sustainable energy transitions, electrification of transportation has emerged as a cornerstone strategy to mitigate dependence on fossil fuels and reduce greenhouse gas emissions (Kaushik et al. 2024; Wang et al. 2023; Xu et al. 2020). Among these efforts, electric vehicles (EVs) have gained remarkable traction, with sales surging from thousands in the early 2010s to millions annually by the 2020s. This accelerating adoption has placed lithium-ion batteries (LIBs) at the center of technological innovation, as they remain the most viable energy storage solution for EVs due to their high efficiency, long cycle life, and scalability (Byeon et al. 2024; Morchhale et al. 2023).

Despite their advantages, LIBs face limitations in energy density and cost, primarily dictated by the properties of cathode materials, which contribute nearly 40% of the total battery cost. Conventional cathode chemistries such as LiCoO_2 , LiFePO_4 , and LiMnO_4 have played significant roles in consumer electronics and early EVs, but their modest specific capacities and limited energy densities restrict their potential for next-generation applications. LiCoO_2 offers good electrochemical stability but suffers from high cost, resource scarcity, and safety concerns. LiFePO_4 provides outstanding stability and long cycle life but is hindered by low conductivity and limited volumetric energy density. LiMnO_4 delivers excellent ionic transport and structural stability, yet its capacity degradation during long-term cycling undermines its viability in high-energy applications (Byeon et al. 2024).

To overcome these constraints, layered oxide cathodes especially nickel-rich lithium nickel-cobalt-manganese oxides ($\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$, NCM) have emerged as the most promising candidates. Ni-rich NCM materials (e.g., NCM811, NCM622, and their derivatives) offer higher reversible capacities ($>200 \text{ mAh g}^{-1}$) and specific energies approaching 800 Wh kg^{-1} , outperforming conventional cathodes. They also provide flexibility in reducing cobalt content, addressing both cost and ethical concerns related to cobalt mining. Notably, Ni-rich compositions, such as those employed in commercial EVs (e.g., Tesla's NCA/NCM chemistries), have demonstrated extended driving ranges and competitive performance metrics (Xu et al. 2024).

However, the high nickel content that enables superior capacity also introduces significant challenges. Ni-rich NCM cathodes are prone to structural instabilities, surface degradation, oxygen release, transition metal dissolution, cation mixing, and particle cracking during cycling. These degradation pathways accelerate capacity fade, reduce safety, and limit commercial scalability. Consequently, developing advanced strategies to stabilize Ni-rich NCM materials has become a focal point of contemporary battery research (Zheng et al. 2023).

In recent years, four primary approaches have gained prominence (Byeon et al. 2024; Li et al. 2024): (i) surface modification, including protective coatings to suppress parasitic reactions; (ii) elemental doping, to reinforce lattice stability and reduce cation disorder; (iii) single-crystal engineering, which mitigates grain boundary failure and improves structural integrity; and (iv) concentration-gradient architectures, which balance mechanical stress and enhance long-term cycling performance. Collectively, these strategies not only extend the practical lifetime of Ni-rich cathodes but also provide critical insights into the fundamental mechanisms of degradation.

This review consolidates and evaluates recent progress in these advanced modification strategies, with emphasis on their mechanisms, advantages, and limitations. By integrating evidence from experimental, the discussion aims to provide a comprehensive framework for understanding the pathways to stabilize Ni-rich NCM cathodes and to guide the design of next-generation high-energy lithium-ion batteries.

2. Methodology

2.1. Data Sources

The primary data for this review were collected from reputable scientific databases, including Scopus, Web of Science, ScienceDirect, SpringerLink, and Google Scholar as a supplementary

source. Only peer-reviewed journal articles, experimental reports, and prior reviews directly related to strategies for improving Nickel–Cobalt–Manganese (NCM) cathode materials in lithium-ion batteries were considered.

2.2. Analytical Approach

A narrative and thematic analysis framework was employed to systematically organize and evaluate the selected literature. The review process involved:

1. Identifying core themes in the existing body of work, particularly focusing on (a) surface modification and coating, (b) doping strategies, (c) single-crystal strategies, and (d) concentration-gradient structures.
2. Categorizing the studies based on structural modification approaches and electrochemical performance (capacity, cycle retention, rate capability, and thermal stability).
3. Comparative assessment of findings across different studies to highlight converging evidence, contrasting outcomes, and emerging research directions.

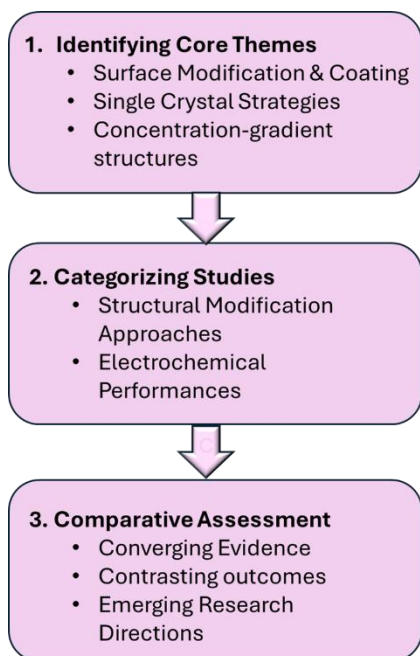


Figure. 1 Flowchart of the Narrative and Thematic Analysis Framework used in the Literature Review.

2.3. Data Analysis

The extracted data were subjected to qualitative synthesis in three stages:

1. Information extraction: key parameters such as electrochemical performance, degradation mechanisms, and mitigation strategies were systematically compiled.
2. Thematic synthesis: the results were clustered into the four primary strategic categories, enabling a structured evaluation of how each approach addresses specific degradation pathways in NCM.
3. Critical evaluation — the strengths, limitations, and feasibility of each strategy were assessed, providing a balanced perspective on current progress and future research opportunities.

This methodological framework ensures a systematic, comprehensive, and critical integration of diverse findings, thereby offering a consolidated understanding of advanced strategies to overcome the persistent issues in NCM cathode materials, as shown in Fig. 2.

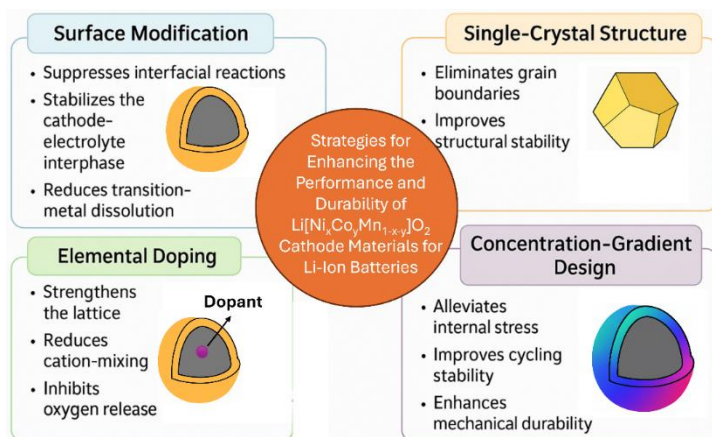


Figure. 2 Schematic Diagram the strategies for Engancing Performance of NCM cathode materials.

3. Results and Discussion

A range of modification strategies has been proposed to suppress degradation phenomena in NCM cathodes (Zhang et al. 2023). Among the most widely applied are surface coatings, elemental substitution, and the development of single-crystal structures (Q. Wu et al. 2020). These methods not only extend the cycling stability of the electrodes but also provide valuable understanding of the underlying degradation pathways. For instance, lattice doping has been shown to enhance structural robustness and reduce phase transitions, while protective coatings minimize surface deterioration and suppress adverse electrolyte interactions, both of which contribute to improved overall battery stability (Li et al. 2024).

The overarching aim of these modifications is to enhance their stability during electrode production and battery cycling, enabling high-energy materials like NCM811, NCM83, and Li-rich NCM to deliver reliable cycle life and performance (Liu et al. 2021). This is particularly significant since Ni-rich NCM cathodes often suffer from limited cycle life, restricting their commercial viability. Each modification strategy targets distinct degradation routes, allowing for precise and optimized improvements in the long-term durability of the materials (Lüther et al. 2024).

3.1. Progresses in the Surface Modification of NCM

Modification of NCM cathode surfaces is commonly achieved by applying a protective layer either on individual particles or entire electrodes or by doping the surface region with foreign ions. A variety of synthesis routes have been explored, including atomic layer deposition (ALD) (Laskar et al. 2017), chemical vapor deposition (CVD) (Xu et al. 2022), magnetron sputtering (Tian et al. 2015), and wet-chemical methods (Zhu et al. 2019). Among these, ALD and CVD typically yield coatings of superior homogeneity, while wet-chemical techniques are favored for large-scale implementation due to their lower cost, despite producing comparatively less uniform layers.

The principal role of surface coatings is to form a chemically and thermodynamically stable barrier on the cathode, thereby reducing interfacial resistance and preserving structural integrity (Liu and Zou 2020). Such protective layers mitigate oxygen release, suppress transition-metal dissolution, and inhibit undesirable phase transformations, while also preventing parasitic reactions and limiting cathode-electrolyte interphase (CEI) formation. Coating materials span a wide range, including electronically conductive carbons, metal oxides (e.g., Al_2O_3 , ZnO , TiO_2 , MgO) (Cheng, Sivonxay, and Persson 2020; Lei et al. 2018), rare-earth oxides, lithium-containing ion conductors (e.g., Li_3PO_4 , LiF , glassy phosphates) (Bandpey et al. 2023), and organic polymers (Li et al. 2023), which can be engineered in either crystalline or amorphous states depending on functional requirements.

Classification of coatings is generally based on their electrical and ionic conductivity (Tang et al. 2023). Even materials with inherently low conductivity are employed when they confer other

benefits such as high mechanical robustness, HF scavenging ability, or superior chemical stability, highlighting the multifunctional role of coatings in stabilizing Ni-rich cathodes (Q. Wu et al. 2020).

3.1.1 Electronically Conductive Coatings

Carbon-based coatings, such as amorphous carbon, graphitic carbon, and graphene oxide have long been employed to improve electronic conductivity while simultaneously protecting the surface from degradation phenomena, including HF-induced corrosion and Mn dissolution (Kucinskis, Bajars, and Kleperis 2013; Park et al. 2010). In addition, conductive polymers such as polypyrrole provide ultrathin and mechanically flexible layers that not only mitigate parasitic interfacial reactions but also accommodate the lattice strain associated with the expansion-contraction behavior of NCM cathodes during cycling (Zhang et al. 2022).

3.1.2 Ionically Conductive Coatings

Li^+ ion conductivity is essential for maintaining rate capability and capacity of NCM cathodes. The application of thin lithium-containing coatings, such as Li_3PO_4 , improves the structural integrity of NCM cathodes by protecting the surface from parasitic electrolyte reactions, while simultaneously promoting Li^+ transport due to their inherent ionic conductivity (Bandpey et al. 2023; Liu et al. 2024). However, excessive coating thickness can obstruct electronic pathways and consequently reduce capacity. Thin Li-containing coatings, such as Li_3PO_4 , improve stability by protecting cathode particles from electrolyte reactions and enhances Li^+ diffusion due to being good Li ion conductor. However, overly thick coatings can reduce capacity by hindering electron transport. Wet-chemical synthesis is commonly used to produce Li_3PO_4 coatings, improving both Li^+ diffusion and cycling performance (Tang et al. 2023).

3.1.3 Non-Conductive Coatings

Non-conductive coatings strengthen both the mechanical and chemical stability of cathode materials by suppressing surface degradation. Nevertheless, if the coating becomes excessively thick, it can hinder electronic and ionic transport, thereby necessitating a careful balance between protective efficiency and electrochemical performance. For example, Al_2O_3 layers have been shown to enhance cycling durability but often lead to a reduction in the initial discharge capacity (Lei et al. 2018). Analogous to Al_2O_3 , TiO_2 coatings protect NCM cathodes by suppressing parasitic reactions with the electrolyte and improving long-term cycling stability. Previous studies reported that although TiO_2 -coated NCM exhibited a decline in initial capacity, the overall durability during cycling was markedly improved (Fan et al. 2020).

It has been reported that, when the coating possesses higher mechanical strength than the cathode particle itself, for instance, amorphous Al_2O_3 with a hardness of up to 13 GPa (Aarik et al. 2022) compared to 11.2 GPa for NCM111 (Cheng et al. 2017), it can effectively reinforce the mechanical integrity of the electrode. Such coatings help mitigate particle volume fluctuations and delay microcrack initiation. However, to preserve electrochemical performance, the coating must allow efficient lithium-ion and electron transport to avoid impedance growth. In addition, an ideal coating material should be both cost-efficient and abundantly available. Therefore, optimizing the thickness of non-conductive coatings is essential to achieving an equilibrium between structural protection and conductive functionality.

3.1.4 Additional Effects of Coatings

In addition to their primary protective functions, surface coatings provide two less commonly highlighted benefits: broadening the electrolyte's electrochemical stability window and facilitating Li-ion transport through interfacial effects. The first mechanism involves the cathode-electrolyte interphase (CEI), which may be intentionally introduced as a coating or spontaneously generated during cycling. The CEI minimizes the mismatch in lithium chemical potential between the electrode and electrolyte at their interface, producing an additional potential drop across the thin interphase layer and thereby extending the electrolyte's electrochemical window (Zhu, He, and Mo 2015).

The second mechanism arises from the formation of a space-charge layer, which develops when two materials with different chemical potentials are brought into contact and charge neutrality cannot be maintained by electron or ion migration alone. This interfacial region exerts a strong influence on Li-ion diffusion and overall ionic conductivity. Depending on the system, the space-charge effect can enhance ion mobility in solid-solid composites or even provide extra mass storage, but it may also hinder conductivity and degrade cell performance. Although its magnitude

ranges from minimal to highly significant, the space-charge layer remains a key factor in the rational design of surface coatings (Cheng et al. n.d.).

3.1.5 Coating and Doping

Chemical coating techniques typically involve a final calcination step to form the targeted protective layer on the cathode surface. For instance, investigations on ZrO₂-coated NCM have shown that annealing above 700 °C promotes Zr⁴⁺ diffusion into the near-surface region of the bulk, effectively resulting in partial doping of the outer lattice (Schipper et al. 2018). In contrast, Al₂O₃ coatings exhibit no detectable Al³⁺ penetration into the NCM bulk, even at annealing temperatures up to 800 °C, which is attributed to the magnetic coupling of transition metals that inhibits aluminium migration (Han et al. 2017).

A thorough analysis of the distribution of coating elements within cathode particles is crucial to distinguish between the effects of coating alone and those resulting from coating combined with doping. Coating is widely recognized for providing surface protection, whereas doping contributes to lattice stabilization within the bulk (Zhang et al. 2023). Prior studies confirm that employing both strategies can deliver complementary improvements, offering simultaneous protection at the surface and stabilization of the bulk structure. However, these modifications are often implemented through separate processes or require distinct precursors for coating and doping. Developing a single modification pathway capable of integrating both effects using the same precursor would enhance overall efficiency by reducing time and cost while achieving the desired improvements in structural integrity and surface stability.

3.2. Progresses Doping Modification of NCM

Ionic doping has been extensively employed to enhance the structural robustness of cathode materials while simultaneously improving their safety performances (Meng, Qu, and Huang 2023; Xu et al. 2024). The primary mechanisms underlying this strategy include (Mohamed and Allam 2020; Tao et al. 2021): (1) promoting Li⁺ diffusion by enlarging the interlayer spacing through dopant incorporation, (2) suppressing Ni²⁺ migration into the lithium layers, thereby reducing cation mixing and maintaining structural order, and (3) mitigating oxygen release by strengthening TM–O bonding and inhibiting unfavorable phase transitions during cycling. Because the performance of ionic doping is strongly influenced by the selection of dopant species, doping techniques, and concentration levels, these parameters must be optimized to maximize the efficiency of high-Ni NCM cathodes. In practice, cation doping typically substitutes either transition-metal or lithium sites, whereas anion doping replaces oxygen atoms, both approaches aiming to stabilize the lattice and limit cation disorder. Various Dopants for Li[Ni_xCo_yMn_{1-x-y}]O₂ layered oxides Cathode Materials are presented in Table 1.

Table 1. Various Dopants for Li[Ni_xCo_yMn_{1-x-y}]O₂ layered oxides Cathode Materials

Dopant	Group	Effects on NCM Performance	Mechanism	Ref.
Y (Yttrium)	Transition Metal, Group 3	↑ Cyclability, ↑ Rate capability, ↑ Capacity retention	Larger ionic radius (Y ³⁺), reduces cation mixing.	(Kalaiselvi and Kalaigan 2019; Kang et al. 2014; Wang et al. 2010)
Ti (Titanium)	Transition Metal, Group 4	↑ Cycle life, ↑ Thermal stability, ↑ Capacity retention	Expands Li ⁺ transport channels, suppresses microcracks, stabilizes Ni ²⁺ migration.	(Du et al. 2015; Song et al. 2018; Sun et al. 2019)
Zr (Zirconium)	Transition Metal, Group 4	↑ Cyclability, ↑ Rate capability, ↑ Thermal stability	Enlarges lattice spacing, reduces TM migration, minimizes oxygen release.	(Ding et al. 2011; Du et al. 2015; Lin et al. 2007)
V (Vanadium)	Transition Metal, Group 5	↑ Structural stability, ↑ Li-ion diffusion, ↑ Rate capability	Multi-valence states stabilize c-axis lattice.	(C. Lu et al. 2016; Sim et al. 2019)

Nb (Niobium)	Transition Metal, Group 5	↑ Rate capability, ↑ Cycle stability	Strong Nb–O bonds, reduces cation mixing, increases inter-slab spacing.	(Li et al. 2020; Yang et al. 2017)
Dopant	Group	Effects on NCM Performance	Mechanism	Ref.
Ta (Tantalum)	Transition Metal, Group 5	↑ Cyclability, ↑ Li-ion diffusion	High valence & strong Ta–O bonds	(Hendri et al. 2024; Yang et al. 2022)
Cr (Chromium)	Transition Metal, Group 6	↑ Cycling stability, ↑ Rate performance	Reduces cation mixing, stabilizes structure.	(Laine et al. 2024; Li et al. 2012)
Mo (Molybdenum)	Transition Metal, Group 6	↑ Capacity, ↑ Thermal & cycle stability	strong Mo–O bonds; stabilizes phase, segregates at grain boundaries; suppresses O release.	(Breuer et al. 2018; Sattar et al. 2020)
W (Tungsten)	Transition Metal, Group 6	↑ Cycling stability, ↑ Thermal stability	Strong W–O bonds, stabilizes layered structure, good at high cutoff voltages (4.5 V).	(Geng et al. 2022; Kim et al. 2018)
Fe (Iron)	Transition Metal, Group 8	↑ Capacity, ↑ cycle stability	Superior structural integrity. Co-doping (Fe/Al, Ti/Fe) improves rate & structure.	(M. Lu et al. 2016; Park et al. 2019)
Cu (Copper)	Transition Metal, Group 11	↑ Li-ion diffusion, ↑ Conductivity, ↑ Capacity retention	Optimal 2 mol% improves cycling stability; reduces cation mixing in Li-rich NCM.	(Milewska and Molenda 2012)
Au (Gold)	Transition Metal, Group 11	↑ Cyclability, ↑ Rate capability	Au nanofibers (2 mol%) improve Li-ion pathways & reduce resistance.	(Yue et al. 2018)
Zn (Zinc)	Transition Metal, Group 12	↑ Cyclability, ↑ Rate capability (but ↓ initial capacity at high content)	Expands lattice spacing; excess Zn → capacity loss. Optimal ~2 mol%.	(Yue et al. 2018)
Cd (Cadmium)	Transition Metal, Group 12	↑ Crystallinity, ↑ Cycling stability	Strong Cd–O bond, increases lattice parameters	(Dong et al. 2019)
Na (Sodium)	Alkali Metal	↑ Lattice expansion, ↑ Rate capability	<3 mol% improves cyclability; excess → void formation.	(Yue et al. 2021)
K (Potassium)	Alkali Metal	↑ Structural stability, ↑ Layer spacing	Acts as “pillar” in Li-layer, reduces cation mixing; excess → lattice distortion.	(Huang et al. 2023; Mo et al. 2020)
Rb (Rubidium)	Alkali Metal	↑ Capacity retention, ↑ Cycling stability	Suppresses O ₂ loss, but excessive Rb → incomplete substitution.	(He et al. 2019; Li et al. 2017)
Mg (Magnesium)	Alkaline Earth Metal	↑ Structural stability, ↑ Capacity retention	Strong Mg–O bonds, reduces resistance, mitigates collapse in NCM811.	(Cho et al. 2017; Ma et al. 2025)

Ca (Calcium)	Alkaline Earth Metal	↑ Stability, ↑ Rate performance	Pillar effect; large ionic radius may cause strain. Optimal ~4.8 mol%.	(Wang et al. 2021)
Dopant	Group	Effects on NCM Performance	Mechanism	Ref.
Ba (Barium)	Alkaline Earth Metal	↑ Conductivity, ↑ Cycling performance	Non-homogeneous distribution; optimal ~8 mol%.	(Wang et al. 2021)
Al (Aluminum)	Post-transition, Group 13	↑ Structural stability, ↑ Cycle life	Strong Al–O bonds; suppresses lattice contraction & microcracks.	(Dang et al. 2022; Jeon et al. 2022)
Ga (Gallium)	Post-transition, Group 13	↑ Cyclability, ↑ Li-ion transport	Expands lattice; Ga/Zr co-doping further boosts kinetics.	(L. Wu et al. 2020)
Sn (Tin)	Post-transition, Group 14	↑ Stability, ↑ Rate performance	Strong Sn–O bonds; excessive Sn → secondary phase & disorder.	(Nguyen et al. 2021)
Pb (Lead)	Post-transition, Group 14	↑ Stability, ↑ Cycle life	Prevents oxygen release in Li-rich NCM; excess → impurities. Optimal ~2 mol%.	(Zhang et al. 2019)
B (Boron)	Metalloid	↑ Stability, ↑ Li-ion migration, ↓ Cracks	Expands cell volume, suppresses rock-salt phase.	(Roitzheim et al. 2022)
Si (Silicon)	Metalloid	↑ Reversible capacity, ↑ Stability	Expands lattice, suppresses phase transitions; effective in Li-rich NCM.	(Weigel et al. 2019)
Ge (Germanium)	Metalloid	↑ Structural stability	Mostly theoretical studies; suppresses O ₂ release, lattice distortion.	(Chen et al. 2021)
Sb (Antimony)	Metalloid	↑ Surface stability, ↑ Cycling	0.1–0.3 mol% beneficial; >0.5 mol% → Sb ₂ O ₃ secondary phase forms coating.	(Li et al. 2019)
La (Lanthanum)	Lanthanide	↑ Stability, ↑ Capacity	Prevents surface degradation in Li-rich NCM.	(Ding et al. 2007; DONG et al. 2017)
Ce (Cerium)	Lanthanide	↑ Stability, ↑ Surface protection	Strong Ce–O bonds;	(ZHONG et al. 2011)
F (Fluorine)	Nonmetal	↑ Stability, ↑ Cycle life	Forms Li–F bonds, enlarges Li-layer spacing, resists HF attack.	(Zhang, Duan, and Zhang 2021)
P (Phosphorus)	Nonmetal	↑ Structural stability	Forms strong PO ₄ ³⁻ bonds	(Yuan et al. 2020)
S (Sulfur)	Nonmetal	↑ Capacity, ↑ Stability	Suppresses phase transitions; effective in Li-rich NCM.	(Lee et al. 2021)
Cl (Chlorine)	Nonmetal	↑ Li-ion diffusion, ↑ Stability	Enlarges Li-layer spacing; co-doping with Br/K effective.	(Hai-Lang Zhang 2013)
Br (Bromine)	Nonmetal	↑ Conductivity, ↑ Stability	Improves ionic/electronic	(Zhu et al. 2018)

			transport; co-doping with Na/Cl effective.	
--	--	--	--	--

3.3. Single Crystal Structure

Single-crystal NCM (SC-NCM) cathodes have gained considerable interest in both academic and industrial fields due to their distinct advantages over polycrystalline NCM (PC-NCM) counterparts (Tao et al. 2021). Key benefits include superior structural integrity, enhanced cycling stability, higher thermal tolerance, and suitability for operation at elevated voltages. Unlike polycrystalline materials, SC-NCM lacks grain boundaries, thereby reducing crack formation. Furthermore, its relatively lower surface area minimizes undesirable interfacial side reactions, phase transformations, and gas evolution, contributing to improved safety and reliability under high-temperature and high-voltage conditions (Park et al. 2018).

Despite these advantages, SC-NCM still encounters several challenges (Li et al. 2022). A primary concern is the reduced lithium-ion diffusion rate within the single-crystal lattice, which can lead to inhomogeneous Li distribution, internal stress buildup, and eventual crack initiation. Fabrication of SC-NCM is also complex and costly, with current high-temperature synthesis processes prone to lithium–nickel cation intermixing. In addition, SC-NCM, similar to other NCM systems, remains vulnerable to issues such as transition-metal dissolution and surface reconstruction.

To address these limitations, various approaches have been proposed, including crystal facet engineering, grain size optimization, elemental doping, and surface/interface modification. Studies indicate that the redox activity of SC-NCM is highly dependent on the state of charge (SOC), with performance markedly enhanced at high SOC when coupled with surface or subsurface modifications. Innovative architectures, such as radially aligned micro-sized particles exposing active crystal planes have demonstrated improved Li-ion transport kinetics, reduced mechanical stress, and superior electrochemical characteristics, including higher capacity and better rate capability. Moreover, the single-crystal morphology enhances thermal stability by mitigating parasitic reactions, thereby ensuring reliable performance under demanding operating conditions (Li et al. 2024).

Comparative investigations further confirm that SC-NCM exhibits stronger resistance to oxygen release, superior cycling durability, and higher energy density compared to polycrystalline analogues. Its long-term stability is particularly notable, with only minor performance degradation over extended cycling. Current research continues to focus on strategies such as heteroatom doping, protective surface coatings, and tailored electrolyte additives to further optimize SC-NCM for high-voltage and high-temperature applications. Nonetheless, substantial progress in processing techniques and cost reduction remains essential before SC-NCM can achieve widespread commercial adoption (Chen et al. 2024).

3.4. Concentration Gradient Structure

When the nickel content exceeds 0.8, the cathode–electrolyte interfacial reactions become unstable, accompanied by pronounced structural contraction during cycling. To mitigate these issues, strategies have been proposed to lower the surface Ni concentration in cathode particles, thereby enhancing their cycling stability (Tao et al. 2021). Three representative structural designs have emerged from this approach: core–shell (CS), core–shell gradient (CSG), and full-concentration gradient (FCG) architectures. These configurations are intended to reinforce structural stability, suppress parasitic interfacial reactions, and alleviate detrimental volume changes.

3.4.1 Core-shell Structure (CS) Cathode: Reduce the Internal Stress Concentration

Sun et al. (Sun et al. 2005) introduced a core–shell cathode architecture consisting of a high-capacity Ni-rich core encased within a structurally stable shell, as exemplified by $\text{Li}[(\text{Ni}_{0.8}\text{Co}_{0.1}\text{Mn}_{0.1})_{0.8}(\text{Ni}_{0.5}\text{Mn}_{0.5})_{0.2}]\text{O}_2$. This configuration delivered a discharge capacity of 188 mAh g⁻¹ within the potential range of 3.0–4.3 V. The shell exerts compressive stress on the Ni-rich core, effectively counterbalancing the tensile stress generated during phase transitions, thereby reducing localized stress accumulation and slowing structural deterioration. Nonetheless, the core experiences more pronounced phase transitions than the shell, creating substantial radial stress at the core–shell interface, which may lead to interfacial debonding. Wu et al. (Wu and Lu

2017) further reported that optimal structural compatibility requires maintaining shell thickness below 0.7 μm , and when the shell is thinner than 0.18 μm , the core radius should not exceed 5 μm to preserve stability and mechanical integrity.

3.4.2 Core-shell Gradient (CSG): Reduce Stress Concentration in the Shell

The introduction of concentration gradients in cathode materials generates a distinctive radial crystallographic texture that overcomes the limitations of conventional designs. Sun et al. (Sun et al. 2005, 2009) proposed Core-shell gradient (CSG) materials with a gradient in the shell, which smooths stress transitions, prevents core-shell debonding, and enhances cyclic stability. Kim et al. (Kim et al. 2019) investigated a $\text{Li}[\text{Ni}_{0.9}\text{Co}_{0.05}\text{Mn}_{0.05}]\text{O}_2$ cathode composed of a $\text{Li}[\text{Ni}_{0.94}\text{Co}_{0.038}\text{Mn}_{0.022}]\text{O}_2$ core surrounded by a 1.5 μm CG shell with a surface composition of $\text{Li}[\text{Ni}_{0.841}\text{Co}_{0.077}\text{Mn}_{0.082}]\text{O}_2$. Their findings demonstrated a gradual phase transition that extended throughout the charging process, in contrast to the abrupt H2→H3 transition characteristic of $\text{Li}[\text{Ni}_{0.9}\text{Co}_{0.05}\text{Mn}_{0.05}]\text{O}_2$ (CS90), thereby stabilizing the c-axis lattice parameter. Furthermore, Kim et al. (Kim et al. 2019) quantified the local compressive stress field arising from anisotropic volume variations. Simulation results indicated that the confining shell enhanced compressive stress in CSG90 particles and promoted a more uniform stress distribution, effectively inhibiting crack propagation. This uniformity is attributed to the elongated, rod-like grains and radially aligned primary particles inherent to CG structures, which help distribute internal forces and block electrolyte infiltration, thereby enhancing mechanical durability.

3.4.3 Full-concentration Gradient (FCG) Cathode: Eliminate Stress Concentration at the Interface of the Core and Shell

Although core-shell gradient (CSG) cathodes exhibit better mechanical robustness than conventional core-shell (CS) structures, the shell thickness is sometimes inadequate to fully preserve structural stability. To overcome this drawback, the full concentration gradient (FCG) design was developed. Sun et al. (Sun et al. 2012) proposed an FCG architecture in which the nickel concentration gradually decreases while the manganese concentration increases from the core toward the particle surface. The FCG-NCM811 cathode showed remarkable cycling performance, maintaining nearly 85% of its capacity after 100 cycles and delivering an initial discharge capacity of 203 mAh g^{-1} (Sun et al. 2012). These findings highlight that the CSG approach significantly improves both the electrochemical capacity and long-term stability of cathode materials.

4. Conclusion

Ni-rich $\text{Li}[\text{Ni}_x\text{Co}_y\text{Mn}_{1-x-y}]\text{O}_2$ cathodes offer exceptional energy density, Positioning them as strong contenders for next-generation lithium-ion batteries. However, their commercialization remains limited by degradation mechanisms such as cation mixing, oxygen release, surface reconstruction, and particle cracking, which impair stability and cycle life. This review highlighted four advanced strategies to address these challenges: surface modification, elemental doping, single-crystal engineering, and concentration-gradient architectures. Collectively, these approaches enhance structural integrity, suppress interfacial degradation, and extend electrochemical durability. Despite notable progress, critical issues remain, including capacity–stability trade-offs, interfacial instability at elevated voltages, and the absence of scalable, cost-effective synthesis methods. Future research must therefore integrate multiple strategies within unified design frameworks while emphasizing industrial scalability and environmental sustainability. In conclusion, holistic material engineering that simultaneously strengthens structural, chemical, and interfacial stability is essential to unlock the full potential of Ni-rich NCM cathodes for safe, high-performance, and commercially viable lithium-ion batteries.

References

- Aarik, Lauri, Hugo Mändar, Aivar Tarre, Helle-Mai Piirsoo, and Jaan Aarik. 2022. "Mechanical Properties of Crystalline and Amorphous Aluminum Oxide Thin Films Grown by Atomic Layer Deposition." *Surface and Coatings Technology* 438:128409. doi: <https://doi.org/10.1016/j.surfcoat.2022.128409>.
- Bandpey, Mohammad, Mehrdad Dorri, Alireza Babaei, Cyrus Zamani, and Mauro Bortolotti. 2023. "Improved Electrochemical Performance of the Cation-Disordered NMC Cathode of Lithium-Ion Batteries by Lithium Phosphate Coating." *ACS Applied Energy Materials* 6(15):7974–84. doi: 10.1021/acsaem.3c01064.

- Breuer, Ortal, Arup Chakraborty, Jing Liu, Tatyana Kravchuk, Larisa Burstein, Judith Grinblat, Yaron Kauffman, Alexandr Gladkih, Prasant Nayak, Merav Tsubery, Anatoly I. Frenkel, Michael Talianker, Dan T. Major, Boris Markovsky, and Doron Aurbach. 2018. "Understanding the Role of Minor Molybdenum Doping in $\text{LiNi}_0.5\text{Co}_0.2\text{Mn}_0.3\text{O}_2$ Electrodes: From Structural and Surface Analyses and Theoretical Modeling to Practical Electrochemical Cells." *ACS Applied Materials and Interfaces* 10(35):29608–21. doi: 10.1021/acsami.8b09795.
- Byeon, Yun Seong, Wontae Lee, Sangbin Park, Dongil Kim, Jaewoo Jung, Min Sik Park, and Won Sub Yoon. 2024. "Comprehensive Understanding of Elemental Doping and Substitution of Ni-Rich Cathode Materials for Lithium-Ion Batteries via In Situ Operando Analyses." *Small Science* 2400165. doi: 10.1002/smssc.202400165.
- Chen, Guanwen, Guannan Qian, Guibin Zan, Michael Lun, Frances Su, Benjamin Stripe, Yong S. Chu, Piero Pianetta, Xiaojing Huang, and Jizhou Li. 2024. "Stabilizing Ni-Rich Layered Cathode for High-Voltage Operation through Hierarchically Heterogeneous Doping with Concentration Gradient." *Materials Today Chemistry* 35(November 2023):101845. doi: 10.1016/j.mtchem.2023.101845.
- Chen, Yan-Hui, Jing Zhang, Yu-Rong Ren, Yi Li, Yong-Fan Zhang, Shu-Ping Huang, Wei Lin, and Wen-Kai Chen. 2021. "Understanding the Role of Various Dopant Metals (Sb, Sn, Ga, Ge, and V) in the Structural and Electrochemical Performances of $\text{LiNi}_0.5\text{Co}_0.2\text{Mn}_0.3\text{O}_2$." *The Journal of Physical Chemistry C* 125(36):19600–608. doi: 10.1021/acs.jpcc.1c04685.
- Cheng, Eric Jianfeng, Kicheol Hong, Nathan John Taylor, Heeman Choe, Jeff Wolfenstine, and Jeff Sakamoto. 2017. "Mechanical and Physical Properties of $\text{LiNi}_0.33\text{Mn}_0.33\text{Co}_0.33\text{O}_2$ (NMC)." *Journal of the European Ceramic Society* 37(9):3213–17. doi: 10.1016/j.jeurceramsoc.2017.03.048.
- Cheng, Jianli, Eric Sivonxay, and Kristin A. Persson. 2020. "Evaluation of Amorphous Oxide Coatings for High-Voltage Li-Ion Battery Applications Using a First-Principles Framework." *ACS Applied Materials and Interfaces* 12(31):35748–56. doi: 10.1021/acsami.0c10000.
- Cheng, Z., M. Liu, S. Ganapathy, C. Li, and Z. Li. n.d. "Revealing the Impact of Space-Charge Layers on the Li-Ion Transport in All-Solid-State Batteries. *Joule* 4, 1311–1323 (2020)."
- Cho, Yongbeom, Myeong Hwan Lee, Hyungsub Kim, Kyojin Ku, Gabin Yoon, Sung Kyun Jung, Byungju Lee, Jongsoo Kim, and Kisuk Kang. 2017. "Activating Layered $\text{LiNi}_0.5\text{Co}_0.2\text{Mn}_0.3\text{O}_2$ as a Host for Mg Intercalation in Rechargeable Mg Batteries." *Materials Research Bulletin* 96:524–32. doi: 10.1016/j.materresbull.2017.04.047.
- Dang, Rongxin, Yuanduo Qu, Zongkai Ma, Lijie Yu, Lianfeng Duan, and Wei Lü. 2022. "The Effect of Elemental Doping on Nickel-Rich NCM Cathode Materials of Lithium Ion Batteries." *Journal of Physical Chemistry C* 126(1):151–59. doi: 10.1021/acs.jpcc.1c09691.
- Ding, C. X., Y. C. Bai, X. Y. Feng, and C. H. Chen. 2011. "Improvement of Electrochemical Properties of Layered $\text{LiNi}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}\text{O}_2$ Positive Electrode Material by Zirconium Doping." *Solid State Ionics* 189(1):69–73. doi: https://doi.org/10.1016/j.ssi.2011.02.015.
- Ding, Yanhuai, Ping Zhang, Yong Jiang, and Deshu Gao. 2007. "Effect of Rare Earth Elements Doping on Structure and Electrochemical Properties of $\text{LiNi}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}\text{O}_2$ for Lithium-Ion Battery." *Solid State Ionics* 178(13):967–71. doi: https://doi.org/10.1016/j.ssi.2007.04.012.
- DONG, Ming-xia, Xiang-qun LI, Zhi-xing WANG, Xin-hai LI, Hua-jun GUO, and Zhen-jun HUANG. 2017. "Enhanced Cycling Stability of La Modified $\text{LiNi}_0.8\text{-XCo}_0.1\text{Mn}_0.1\text{La}_x\text{O}_2$ for Li-Ion Battery." *Transactions of Nonferrous Metals Society of China* 27(5):1134–42. doi: https://doi.org/10.1016/S1003-6326(17)60132-8.
- Dong, Shengde, Yuan Zhou, Chunxi Hai, Jinbo Zeng, Yanxia Sun, Yue Shen, Xiang Li, Xiufeng Ren, Guicai Qi, and Luxiang Ma. 2019. "Solvothermally Synthesized $\text{Li}(\text{Ni}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2})\text{XCd}_1\text{-XO}_2$ Cathode Materials with Excellent Electrochemical Performance for Lithium-Ion Batteries." *Ionics* 25(12):5655–67. doi: 10.1007/s11581-019-03106-1.
- Du, Rui, Yujing Bi, Wenchao Yang, Zhe Peng, Meng Liu, Yang Liu, Baoming Wu, Bangcheng Yang, Fei Ding, and Deyu Wang. 2015. "Improved Cyclic Stability of $\text{LiNi}_0.8\text{Co}_0.1\text{Mn}_{0.1}\text{O}_2$ via Ti Substitution with a Cut-off Potential of 4.5V." *Ceramics International* 41(5, Part B):7133–39. doi: https://doi.org/10.1016/j.ceramint.2015.02.026.
- Fan, Qinglu, Kaiji Lin, Shaodian Yang, Shoujie Guan, Jinbiao Chen, Shuai Feng, Jun Liu, Liying Liu, Jie Li, and Zhicong Shi. 2020. "Constructing Effective TiO_2 Nano-Coating for High-Voltage Ni-Rich Cathode Materials for Lithium Ion Batteries by Precise Kinetic Control." *Journal of Power Sources* 477:228745. doi: https://doi.org/10.1016/j.jpowsour.2020.228745.
- Geng, Chenxi, Divya Rathore, Dylan Heino, Ning Zhang, Ines Hamam, Nafiseh Zaker, Gianluigi A. Botton, Roee Omessi, Nutthaphon Phattharasupakun, and Toby Bond. 2022. "Mechanism of

- Action of the Tungsten Dopant in LiNiO₂ Positive Electrode Materials." *Advanced Energy Materials* 12(6):2103067.
- Hai-Lang Zhang, Shuixiang Liu. 2013. "Synthesis and Characterization of LiNi_{1/3}Co_{1/3}Mn_{1/3}O_{2-x}Cl_x as Cathode Materials for Lithium Ion Batteries at 55°C." *Advances in Materials Science and Engineering*.
- Han, Binghong, Tadas Paulauskas, Baris Key, Cameron Peebles, Joong Sun Park, Robert F. Klie, John T. Vaughey, and Fulya Dogan. 2017. "Understanding the Role of Temperature and Cathode Composition on Interface and Bulk: Optimizing Aluminum Oxide Coatings for Li-Ion Cathodes." *ACS Applied Materials & Interfaces* 9(17):14769–78.
- He, Tao, Lai Chen, Yuefeng Su, Yun Lu, Liying Bao, Gang Chen, Qiyu Zhang, Shi Chen, and Feng Wu. 2019. "The Effects of Alkali Metal Ions with Different Ionic Radii Substituting in Li Sites on the Electrochemical Properties of Ni-Rich Cathode Materials." *Journal of Power Sources* 441:227195. doi: <https://doi.org/10.1016/j.jpowsour.2019.227195>.
- Hendri, Yola Bertilsya, Liang Yin Kuo, Manojkumar Seenivasan, Yi Shiuan Wu, She Huang Wu, Jeng Kuei Chang, Rajan Jose, Martin Ihrig, Payam Kaghazchi, and Chun Chen Yang. 2024. "Two Birds with One Stone: One-Pot Concurrent Ta-Doping and -Coating on Ni-Rich LiNi_{0.92}Co_{0.04}Mn_{0.04}O₂ Cathode Materials with Fiber-Type Microstructure and Li+-Conducting Layer Formation." *Journal of Colloid and Interface Science* 661(November 2023):289–306. doi: [10.1016/j.jcis.2024.01.094](https://doi.org/10.1016/j.jcis.2024.01.094).
- Huang, Zhi Xiong, Zhen Yi Gu, Yong Li Heng, Edison Huixiang Ang, Hong Bo Geng, and Xing Long Wu. 2023. "Advanced Layered Oxide Cathodes for Sodium/Potassium-Ion Batteries: Development, Challenges and Prospects." *Chemical Engineering Journal* 452(P3):139438. doi: [10.1016/j.cej.2022.139438](https://doi.org/10.1016/j.cej.2022.139438).
- Jeon, Hyungkwon, Soonhyun Hong, Minjeong Kim, Jahun Koo, Heesang Lee, Gyuseok Choi, and Chunjoong Kim. 2022. "Synthesis of Ni-Rich NCMA Precursor through Co-Precipitation and Improvement of Cycling through Boron and Sn Doping." *Korean Journal of Materials Research* 32(4):210–15. doi: [10.3740/MRSK.2022.32.4.210](https://doi.org/10.3740/MRSK.2022.32.4.210).
- Kalaiselvi, K., and G. Paruthimal Kalaigan. 2019. "Yttrium-Substituted LiNiO. 3Mn0. 3Co0. 3O2 Cathode Material with Enhanced Cycling Stability for Rechargeable Lithium-Ion Batteries." *Ionics* 25(3):991–97.
- Kang, Shifei, Hengfei Qin, Yao Fang, Xi Li, and Yangang Wang. 2014. "Preparation and Electrochemical Performance of Yttrium-Doped Li[Li_{0.20}Mn_{0.534}Ni_{0.133}Co_{0.133}]O₂ as Cathode Material for Lithium-Ion Batteries." *Electrochimica Acta* 144:22–30. doi: <https://doi.org/10.1016/j.electacta.2014.06.155>.
- Kaushik, Shruti, Tushar Mehta, Prakash Chand, Swati Sharma, and Gulshan Kumar. 2024. "Recent Advancements in Cathode Materials for High-Performance Li-Ion Batteries: Progress and Prospects." *Journal of Energy Storage* 97(PA):112818. doi: [10.1016/j.est.2024.112818](https://doi.org/10.1016/j.est.2024.112818).
- Kim, U. H., D. W. Jun, K. J. Park, Q. Zhang, P. Kaghazchi, D. Aurbach, D. T. Major, G. Goobes, M. Dixit, N. Leifer, C. M. Wang, P. Yan, D. Ahn, K. H. Kim, C. S. Yoon, and Y. K. Sun. 2018. "Pushing the Limit of Layered Transition Metal Oxide Cathodes for High-Energy Density Rechargeable Li Ion Batteries." *Energy and Environmental Science* 11(5):1271–79. doi: [10.1039/c8ee00227d](https://doi.org/10.1039/c8ee00227d).
- Kim, Un Hyuck, Hoon Hee Ryu, Jae Hyung Kim, Robert Mücke, Payam Kaghazchi, Chong S. Yoon, and Yang Kook Sun. 2019. "Microstructure-Controlled Ni-Rich Cathode Material by Microscale Compositional Partition for Next-Generation Electric Vehicles." *Advanced Energy Materials* 9(15):1–11. doi: [10.1002/aenm.201803902](https://doi.org/10.1002/aenm.201803902).
- Kucinskis, Gints, Gunars Bajars, and Janis Kleperis. 2013. "Graphene in Lithium Ion Battery Cathode Materials: A Review." *Journal of Power Sources* 240:66–79. doi: <https://doi.org/10.1016/j.jpowsour.2013.03.160>.
- Laine, Petteri, Juho Välikangas, Toni Kauppinen, Tao Hu, Shubo Wang, Graham King, Harishchandra Singh, Pekka Tynjälä, and Ulla Lassi. 2024. "Synergistic Effects of Low - Level Magnesium and Chromium Doping on the Electrochemical Performance of LiNiO₂ Cathodes." *Journal of Solid State Electrochemistry* 28(1):85–101.
- Laskar, Masihur R., David H. K. Jackson, Shenzen Xu, Robert J. Hamers, Dane Morgan, and Thomas F. Kuech. 2017. "Atomic Layer Deposited MgO: A Lower Overpotential Coating for Li [Ni_{0.5}Mn_{0.3}Co_{0.2}] O₂ Cathode." *ACS Applied Materials & Interfaces* 9(12):11231–39.
- Lee, Jimin, Sanghyuk Park, Mincheol Beak, Sang R. Park, Ah R. Lee, Suk H. Byun, Junho Song, Jeong S. Sohn, and Kyungjung Kwon. 2021. "The Effect of Excessive Sulfate in the Li-Ion Battery Leachate on the Properties of Resynthesized Li[Ni_{1/3}Co_{1/3}Mn_{1/3}]O₂." *Materials* 14(21).
- Lei, Tongxing, Yunjiao Li, Qianye Su, Guolin Cao, Wei Li, Yongxiang Chen, Longlong Xue, and Shiyi Deng. 2018. "High-Voltage Electrochemical Performance of LiNi_{0.5}Co_{0.2}Mn_{0.3}O₂

- Cathode Materials via Al Concentration Gradient Modification." *Ceramics International* 44(8):8809–17. doi: 10.1016/j.ceramint.2018.02.053.
- Li, Jing, Maolin Zhang, Dongyan Zhang, Yangxi Yan, and Zhimin Li. 2020. "An Effective Doping Strategy to Improve the Cyclic Stability and Rate Capability of Ni-Rich $\text{LiNi}_{0.8}\text{Co}_{0.1}\text{Mn}_{0.1}\text{O}_2$ Cathode." *Chemical Engineering Journal* 402(March):126195. doi: 10.1016/j.cej.2020.126195.
- Li, Jing, Wentao Zhong, Qiang Deng, Qimeng Zhang, and Chenghao Yang. 2022. "Recent Progress in Synthesis and Surface Modification of Nickel-Rich Layered Oxide Cathode Materials for Lithium-Ion Batteries." *International Journal of Extreme Manufacturing* 4(4). doi: 10.1088/2631-7990/ac92ef.
- Li, Ling-jun, Zhi-Xing Wang, Qi-Cheng Liu, Chang Ye, Zhao-Yong Chen, and Li Gong. 2012. "Effects of Chromium on the Structural, Surface Chemistry and Electrochemical of Layered $\text{LiNi}_{0.8-x}\text{Co}_{0.1}\text{Mn}_{0.1}\text{Cr}_x\text{O}_2$." *Electrochimica Acta* 77:89–96. doi: <https://doi.org/10.1016/j.electacta.2012.05.076>.
- Li, Nan, Yu-Shi He, Xiaoping Wang, Weimin Zhang, Zi-Feng Ma, and Dongyun Zhang. 2017. "Incorporation of Rubidium Cations into $\text{Li}_{1.2}\text{Mn}_{0.54}\text{Co}_{0.13}\text{Ni}_{0.13}\text{O}_2$ Layered Oxide Cathodes for Improved Cycling Stability." *Electrochimica Acta* 231:363–70. doi: <https://doi.org/10.1016/j.electacta.2017.01.137>.
- Li, Tiantian, Xiangran Chang, Yan Xin, Yang Liu, and Huajun Tian. 2023. "Synergistic Strategy Using Doping and Polymeric Coating Enables High-Performance High-Nickel Layered Cathodes for Lithium-Ion Batteries." *Journal of Physical Chemistry C* 127(18):8448–61. doi: 10.1021/acs.jpcc.3c00951.
- Li, Yue, Zhouliang Tan, Yuming Liu, Changlong Lei, Peipei He, Jingyi Li, Zhenjiang He, Yi Cheng, Feixiang Wu, and Yunjiao Li. 2024. "Past, Present and Future of High-Nickel Materials." *Nano Energy* 119(November 2023):109070. doi: 10.1016/j.nanoen.2023.109070.
- Li, Yunjiao, Jie Zhu, Shiyi Deng, Tongxing Lei, Yongxiang Chen, Guolin Cao, Shilei Wang, Jinping Zhang, and Jia Guo. 2019. "Towards Superior Cyclability of $\text{LiNi}_{0.8}\text{Co}_{0.1}\text{Mn}_{0.1}\text{O}_2$ Cathode Material for Lithium Ion Batteries via Synergetic Effects of Sb Modification." *Journal of Alloys and Compounds* 798:93–103.
- Lin, Bin, Zhaoyin Wen, Zhonghua Gu, and Xiaoxiong Xu. 2007. "Preparation and Electrochemical Properties of $\text{Li}[\text{Ni}_{1/3}\text{Co}_{1/3}\text{Mn}_{1-x}/3\text{Zr}_x/3]\text{O}_2$ Cathode Materials for Li-Ion Batteries." *Journal of Power Sources* 174(2):544–47. doi: <https://doi.org/10.1016/j.jpowsour.2007.06.125>.
- Liu, Jie, and Zhengguang Zou. 2020. "Structure, Modification, and Commercialization of High Nickel Ternary Material ($\text{LiNi}_{0.8}\text{Co}_{0.1}\text{Mn}_{0.1}\text{O}_2$ and $\text{LiNi}_{0.8}\text{Co}_{0.15}\text{Al}_{0.05}\text{O}_2$) for Lithium Ion Batteries." *Journal of Solid State Electrochemistry* 25:387–410. doi: DOI: 10.1007/s10008-020-04818-5.
- Liu, Junxiang, Jiaqi Wang, Youxuan Ni, Kai Zhang, Fangyi Cheng, and Jun Chen. 2021. "Recent Breakthroughs and Perspectives of High-Energy Layered Oxide Cathode Materials for Lithium Ion Batteries." *Materials Today* 43(March):132–65. doi: 10.1016/j.mattod.2020.10.028.
- Liu, Wanmin, Sisha Zeng, Piaopiao Wang, Jing Huang, Bin Shen, Mulan Qin, Weigang Wang, and Zexun Tang. 2024. "Dual-Coated Single-Crystal $\text{LiNi}_{0.6}\text{Co}_{0.2}\text{Mn}_{0.2}\text{O}_2$ as High-Performance Cathode Materials for Lithium-Ion Batteries." *Journal of Solid State Electrochemistry* (0123456789):0–7. doi: 10.1007/s10008-024-06048-5.
- Lu, Chao, Shiqing Yang, Hao Wu, Yun Zhang, Xingjiang Yang, and Taohua Liang. 2016. "Enhanced Electrochemical Performance of Li-Rich $\text{Li}_{1.2}\text{Mn}_{0.52}\text{Co}_{0.08}\text{Ni}_{0.2}\text{O}_2$ Cathode Materials for Li-Ion Batteries by Vanadium Doping." *Electrochimica Acta* 209:448–55. doi: <https://doi.org/10.1016/j.electacta.2016.05.119>.
- Lu, Min, Enshan Han, Lingzhi Zhu, Sen Chen, and Guangquan Zhang. 2016. "The Effects of Ti^{4+} - Fe^{3+} Co-Doping on $\text{Li}[\text{Ni}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}]\text{O}_2$." *Solid State Ionics* 298:9–14. doi: <https://doi.org/10.1016/j.ssi.2016.10.014>.
- Lüther, Marco Joes, Shi Kai Jiang, Martin Alexander Lange, Julius Buchmann, Aurora Gómez Martín, Richard Schmuck, Tobias Placke, Bing Joe Hwang, Martin Winter, and Johannes Kasnatscheew. 2024. "Systematic 'Apple-to-Apple' Comparison of Single-Crystal and Polycrystalline Ni-Rich Cathode Active Materials: From Comparable Synthesis to Comparable Electrochemical Conditions." *Small Structures* 2400119:1–12. doi: 10.1002/sstr.202400119.
- Ma, Jianyao, Xin Huang, Ruijian Huang, Yang Tang, Shengyi Huang, Yuhang Wang, Bin Huang, Jianwen Yang, Yanwei Li, Meng Qin, and Shunhua Xiao. 2025. "An Ultra-High Nickel Cobalt-Free Cathode Material toward High-Energy and Long-Cycle Stable Li-Ion Batteries: A Single-Crystal and Surface High-Entropy Design Strategy." *Journal of Materials Chemistry A*. doi: 10.1039/d5ta01897h.

- Meng, Jingke, Ge Qu, and Yunhui Huang. 2023. "Stabilization Strategies for High-Capacity NCM Materials Targeting for Safety and Durability Improvements." *ETransportation* 16(August 2022). doi: 10.1016/j.etrans.2023.100233.
- Milewska, A., and J. Molenda. 2012. "Influence of Co Substitution and Cu Addition on Structural, Electrical, Tran[1] A. Milewska, J. Molenda, Solid State Ionics 2012, 225, 551.Sport and Electrochemical Properties of $\text{Li}_x\text{Ni}_{0.9-y}\text{Co}_y\text{Mn}_{0.102}$ Cathode Materials." *Solid State Ionics* 225:551–55. doi: <https://doi.org/10.1016/j.ssi.2012.02.030>.
- Mo, Yan, Lingjun Guo, Baodong Du, Hongfei Jin, Bokai Cao, Yang Lu, De Li, and Yong Chen. 2020. "The Promotion of Phase Transitions for Ni-Based Layered Cathode towards Enhanced High-Voltage Cycle Stability." *Journal of Power Sources* 477(July). doi: 10.1016/j.jpowsour.2020.228699.
- Mohamed, Nourhan, and Nageh K. Allam. 2020. "Recent Advances in the Design of Cathode Materials for Li-Ion Batteries." *RSC Advances* 10(37):21662–85. doi: 10.1039/d0ra03314f.
- Morchhale, Ayush, Zhenghuan Tang, Chanyeop Yu, Rashid Farahati, and Jung Hyun Kim. 2023. "Coating Materials and Processes for Cathodes in Sulfide-Based All Solid-State Batteries." *Current Opinion in Electrochemistry* 39:101251. doi: 10.1016/j.coelec.2023.101251.
- Nguyen, Trung Thien, Un-Hyuck Kim, Chong S. Yoon, and Yang-Kook Sun. 2021. "Enhanced Cycling Stability of Sn-Doped Li $[\text{Ni}_{0.90}\text{Co}_{0.05}\text{Mn}_{0.05}]\text{O}_2$ via Optimization of Particle Shape and Orientation." *Chemical Engineering Journal* 405:126887.
- Park, Kang Joon, Hun Gi Jung, Liang Yin Kuo, Payam Kaghazchi, Chong S. Yoon, and Yang Kook Sun. 2018. "Improved Cycling Stability of $\text{Li}[\text{Ni}_{0.90}\text{Co}_{0.05}\text{Mn}_{0.05}]\text{O}_2$ Through Microstructure Modification by Boron Doping for Li-Ion Batteries." *Advanced Energy Materials* 8(25):0–9. doi: 10.1002/aenm.201801202.
- Park, Myounggu, Xiangchun Zhang, Myoungdo Chung, Gregory B. Less, and Ann Marie Sastry. 2010. "A Review of Conduction Phenomena in Li-Ion Batteries." *Journal of Power Sources* 195(24):7904–29. doi: <https://doi.org/10.1016/j.jpowsour.2010.06.060>.
- Park, Sanghyuk, Duho Kim, Heesuk Ku, Minsang Jo, Sangjun Kim, Junho Song, Jisang Yu, and Kyungjung Kwon. 2019. "The Effect of Fe as an Impurity Element for Sustainable Resynthesis of $\text{Li}[\text{Ni}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}]\text{O}_2$ Cathode Material from Spent Lithium-Ion Batteries." *Electrochimica Acta* 296:814–22. doi: 10.1016/j.electacta.2018.11.001.
- Roitzheim, Christoph, Liang Yin Kuo, Yoo Jung Sohn, Martin Finsterbusch, Sören Möller, Doris Sebold, Helen Valencia, Maria Meledina, Joachim Mayer, Uwe Breuer, Payam Kaghazchi, Olivier Guillon, and Dina Fattakhova-Rohlfing. 2022. "Boron in Ni-Rich NCM811 Cathode Material: Impact on Atomic and Microscale Properties." *ACS Applied Energy Materials* 5(1):524–38. doi: 10.1021/acsaem.1c03000.
- Sattar, Tahir, Seung Hwan Lee, Bong Soo Jin, and Hyun Soo Kim. 2020. "Influence of Mo Addition on the Structural and Electrochemical Performance of Ni-Rich Cathode Material for Lithium-Ion Batteries." *Scientific Reports* 10(1):4–13. doi: 10.1038/s41598-020-64546-8.
- Schipper, Florian, Hana Bouzaglo, Mudit Dixit, Evan M. Erickson, Tina Weigel, Michael Talianker, Judith Grinblat, Larisa Burstein, Michael Schmidt, and Jordan Lampert. 2018. "From Surface ZrO_2 Coating to Bulk Zr Doping by High Temperature Annealing of Nickel-rich Lithiated Oxides and Their Enhanced Electrochemical Performance in Lithium Ion Batteries." *Advanced Energy Materials* 8(4):1701682.
- Sim, Seung Ju, Seung Hwan Lee, Bong Soo Jin, and Hyun Soo Kim. 2019. "Improving the Electrochemical Performances Using a V-Doped Ni-Rich NCM Cathode." *Scientific Reports* 9(1):1–8. doi: 10.1038/s41598-019-45556-7.
- Song, Jun-Ho, Joongho Bae, Ko-woon Lee, Ilbok Lee, Keebum Hwang, Woosuk Cho, Sang June Hahn, and Songhun Yoon. 2018. "Enhancement of High Temperature Cycling Stability in High-Nickel Cathode Materials with Titanium Doping." *Journal of Industrial and Engineering Chemistry* 68:124–28. doi: <https://doi.org/10.1016/j.jiec.2018.07.036>.
- Sun, Huabin, Zhilin Cao, Tengrui Wang, Rui Lin, Yuyu Li, Xi Liu, Lulu Zhang, Feng Lin, Yunhui Huang, and Wei Luo. 2019. "Enabling High Rate Performance of Ni-Rich Layered Oxide Cathode by Uniform Titanium Doping." *Materials Today Energy* 13:145–51. doi: <https://doi.org/10.1016/j.mtener.2019.05.003>.
- Sun, Yang-Kook, Seung-Taek Myung, Myung-Hoon Kim, Jai Prakash, and Khalil Amine. 2005. "Synthesis and Characterization of Li $[(\text{Ni}_{0.8}\text{Co}_{0.1}\text{Mn}_{0.1})_{0.8}(\text{Ni}_{0.5}\text{Mn}_{0.5})_{0.2}]\text{O}_2$ with the Microscale Core–Shell Structure as the Positive Electrode Material for Lithium Batteries." *Journal of the American Chemical Society* 127(38):13411–18.
- Sun, Yang-Kook, Seung-Taek Myung, Byung-Chun Park, Jai Prakash, Ilias Belharouak, and Khalil Amine. 2009. "High-Energy Cathode Material for Long-Life and Safe Lithium Batteries." *Nature Materials* 8(4):320–24.
- Sun, Yang Kook, Zonghai Chen, Hyung Joo Noh, Dong Ju Lee, Hun Gi Jung, Yang Ren, Steve

- Wang, Chong Seung Yoon, Seung Taek Myung, and Khalil Amine. 2012. "Nanostructured High-Energy Cathode Materials for Advanced Lithium Batteries." *Nature Materials* 11(11):942–47. doi: 10.1038/nmat3435.
- Tang, Zhongfeng, Dandan Feng, Yali Xu, Lei Chen, Xiangdan Zhang, and Qiang Ma. 2023. "Safety Issues of Layered Nickel-Based Cathode Materials for Lithium-Ion Batteries: Origin, Strategies and Prospects." *Batteries* 9(3). doi: 10.3390/batteries9030156.
- Tao, Qiqi, Liguang Wang, Caihong Shi, Jun Li, Guang Chen, Zheng Xue, Jichang Wang, Shun Wang, and Huile Jin. 2021. "Understanding the Ni-Rich Layered Structure Materials for High-Energy Density Lithium-Ion Batteries." *Materials Chemistry Frontiers* 5(6):2607–22. doi: 10.1039/d1qm00052g.
- Tian, Ruiyuan, Haiqiang Liu, Yi Jiang, Jiankun Chen, Xinghua Tan, Guangyao Liu, Lina Zhang, Xiaohua Gu, Yanjun Guo, and Hanfu Wang. 2015. "Drastically Enhanced High-Rate Performance of Carbon-Coated LiFePO₄ Nanorods Using a Green Chemical Vapor Deposition (CVD) Method for Lithium Ion Battery: A Selective Carbon Coating Process." *ACS Applied Materials & Interfaces* 7(21):11377–86.
- Wang, Jiayi, Xincheng Lei, Shengnan Guo, Lin Gu, Xin Wang, Aiping Yu, and Dong Su. 2023. "Doping Strategy in Nickel-Rich Layered Oxide Cathode for Lithium-Ion Battery." *Renewables* 1(3):316–40. doi: 10.31635/renewables.023.202200022.
- Wang, Meng, Yunbo Chen, Feng Wu, Yuefeng Su, Lin Chen, and Dongliang Wang. 2010. "Characterization of Yttrium Substituted LiNi_{0.33}Mn_{0.33}Co_{0.33}O₂ Cathode Material for Lithium Secondary Cells." *Electrochimica Acta* 55(28):8815–20. doi: 10.1016/j.electacta.2010.08.022.
- Wang, Yang-Yang, Xiang Song, Sheng Liu, Guo-Ran Li, Shi-Hai Ye, and Xue-Ping Gao. 2021. "Elucidating the Effect of the Dopant Ionic Radius on the Structure and Electrochemical Performance of Ni-Rich Layered Oxides for Lithium-Ion Batteries." *ACS Applied Materials & Interfaces* 13(47):56233–41. doi: 10.1021/acsami.1c17991.
- Weigel, Tina, Florian Schipper, Evan M. Erickson, Francis Amalraj Susai, Boris Markovsky, and Doron Aurbach. 2019. "Structural and Electrochemical Aspects of LiNi_{0.8}Co_{0.1}Mn_{0.1}O₂ Cathode Materials Doped by Various Cations." *ACS Energy Letters* 4(2):508–16.
- Wu, Bin, and Wei Lu. 2017. "Mechanical Modeling of Particles with Active Core–Shell Structures for Lithium-Ion Battery Electrodes." *The Journal of Physical Chemistry C* 121(35):19022–30.
- Wu, Liping, Xincun Tang, Xi Chen, Zhihao Rong, Wei Dang, Yang Wang, Xing Li, Liuchun Huang, and Yi Zhang. 2020. "Improvement of Electrochemical Reversibility of the Ni-Rich Cathode Material by Gallium Doping." *Journal of Power Sources* 445:227337. doi: https://doi.org/10.1016/j.jpowsour.2019.227337.
- Wu, Qian, Shulan Mao, Zhuoya Wang, Yang Tong, and Yingying Lu. 2020. "Improving LiNi_xCo_yMn_{1-x-y}O₂ Cathode Electrolyte Interface under High Voltage in Lithium Ion Batteries." *Nano Select* 1(1):111–34. doi: 10.1002/nano.202000008.
- Xu, Gui Liang, Xiang Liu, Amine Daali, Rachid Amine, Zonghai Chen, and Khalil Amine. 2020. "Challenges and Strategies to Advance High-Energy Nickel-Rich Layered Lithium Transition Metal Oxide Cathodes for Harsh Operation." *Advanced Functional Materials* 30(46). doi: 10.1002/adfm.202004748.
- Xu, Tianmei, Jingjing Wu, Juan Ding, Yingde Huang, Yudai Huang, and Wengao Zhao. 2024. "Advancements in Addressing Microcrack Formation in Ni-Rich Layered Oxide Cathodes for Lithium-Ion Batteries." *ChemElectroChem* c:1–8. doi: 10.1002/celec.202300802.
- Xu, Yuanlai, Tianyu Pan, Fuchuan Liu, Pei Zhao, Xingmao Jiang, and Chunyan Xiong. 2022. "Surface Coating and Doping of Single-Crystal LiNi_{0.5}Co_{0.2}Mn_{0.3}O₂ for Enhanced High-Voltage Electrochemical Performances via Chemical Vapor Deposition." *Journal of Electroanalytical Chemistry* 914:116286. doi: https://doi.org/10.1016/j.jelechem.2022.116286.
- Yang, Wen, Haodong Li, Dong Wang, Chunliu Xu, Wei Xiang, Yang Song, Fengrong He, Jun Zhang, Baoping Zheng, Benhe Zhong, Zhenguo Wu, and Xiaodong Guo. 2022. "Ta Induced Fine Tuning of Microstructure and Interface Enabling Ni-Rich Cathode with Unexpected Cyclability in Pouch-Type Full Cell." *Nano Energy* 104:107880. doi: https://doi.org/10.1016/j.nanoen.2022.107880.
- Yang, Zuguang, Wei Xiang, Zhenguo Wu, Fengrong He, Jun Zhang, Yao Xiao, Benhe Zhong, and Xiaodong Guo. 2017. "Effect of Niobium Doping on the Structure and Electrochemical Performance of LiNi_{0.5}Co_{0.2}Mn_{0.3}O₂ Cathode Materials for Lithium Ion Batteries." *Ceramics International* 43(4):3866–72. doi: 10.1016/j.ceramint.2016.12.048.
- Yuan, An, Hao Tang, Li Liu, Jin Ying, Lian Tan, Long Tan, and Runguang Sun. 2020. "High Performance of Phosphorus and Fluorine Co-Doped LiNi_{0.8}Co_{0.1}Mn_{0.1}O₂ as a Cathode Material for Lithium Ion Batteries." *Journal of Alloys and Compounds* 844:156210. doi:

- <https://doi.org/10.1016/j.jallcom.2020.156210>.
- Yue, Bin, Xinlu Wang, Jinxian Wang, Jing Yao, Xinru Zhao, Hongbo Zhang, Wensheng Yu, Guixia Liu, and Xiangting Dong. 2018. "Au-Doped $\text{Li}_{1.2}\text{Ni}_{0.7}\text{Co}_{0.1}\text{Mn}_{0.2}\text{O}_2$ Electrospun Nanofibers: Synthesis and Enhanced Capacity Retention Performance for Lithium-Ion Batteries." *RSC Advances* 8(8):4112–18. doi: 10.1039/C7RA12705G.
- Yue, Ruyun, Fang Xia, Ruijuan Qi, Da Tie, Shanshan Shi, Zhiping Li, Yufeng Zhao, and Jiujuun Zhang. 2021. "Trace Nb-Doped $\text{Na}_{0.7}\text{Ni}_{0.3}\text{Co}_{0.1}\text{Mn}_{0.6}\text{O}_2$ with Suppressed Voltage Decay and Enhanced Low Temperature Performance." *Chinese Chemical Letters* 32(2):849–53. doi: 10.1016/j.ccllet.2020.05.025.
- Zhang, Xiaozhen, Gaopan Liu, Ke Zhou, Tianpeng Jiao, Yue Zou, Qilong Wu, Xunxin Chen, Yong Yang, and Jianming Zheng. 2022. "Enhancing Cycle Life of Nickel-Rich $\text{LiNi}_{0.9}\text{Co}_{0.05}\text{Mn}_{0.05}\text{O}_2$ via a Highly Fluorinated Electrolyte Additive - Pentafluoropyridine." *Energy Materials* 1(1):100005. doi: 10.20517/energymater.2021.07.
- Zhang, Xueqian, Yali Xiong, Mengfei Dong, and Zhiguo Hou. 2019. "Pb-Doped Lithium-Rich Cathode Material for High Energy Density Lithium-Ion Full Batteries." *Journal of The Electrochemical Society* 166(13):A2960. doi: 10.1149/2.0860913jes.
- Zhang, Yafeng, Ling Duan, and Jiajia Zhang. 2021. "Superior Electrochemical Properties of Zirconium and Fluorine Co-doped $\text{Li}_{1.20}[\text{Mn}_{0.54}\text{Ni}_{0.13}\text{Co}_{0.13}]\text{O}_2$ as Cathode Material for Lithium Ion Batteries." *Journal of Materials Science: Materials in Electronics* 32(4):4380–92. doi: 10.1007/s10854-020-05181-x.
- Zhang, Yuxuan, Jae Chul Kim, Han Wook Song, and Sunghwan Lee. 2023. "Recent Achievements toward the Development of Ni-Based Layered Oxide Cathodes for Fast-Charging Li-Ion Batteries." *Nanoscale* 15(9):4195–4218. doi: 10.1039/d2nr05701h.
- Zheng, Xiangyi, Zhao Cai, Jie Sun, Jianhao He, Wenjin Rao, Jing Wang, Yuxiang Zhang, Qiang Gao, Bo Han, Kaisheng Xia, Ruimin Sun, and Chenggang Zhou. 2023. "Nickel-Rich Layered Oxide Cathodes for Lithium-Ion Batteries: Failure Mechanisms and Modification Strategies." *Journal of Energy Storage* 58(July 2022):106405. doi: 10.1016/j.est.2022.106405.
- ZHONG, Shengkui, You WANG, Jiequn LIU, Kang WAN, and Fan LÜ. 2011. "Synthesis and Electrochemical Properties of Ce-Doped $\text{LiNi}_{1/3}\text{Mn}_{1/3}\text{Co}_{1/3}\text{O}_2$ Cathode Material for Li-Ion Batteries." *Journal of Rare Earths* 29(9):891–95. doi: [https://doi.org/10.1016/S1002-0721\(10\)60562-5](https://doi.org/10.1016/S1002-0721(10)60562-5).
- Zhu, Huali, Qifeng Li, Xiaolong Gong, Kaifeng Cao, and Zhaoyong Chen. 2018. "Enhanced High Voltage Performance of Chlorine/Bromine Co-Doped Lithium Nickel Manganese Cobalt Oxide." *Crystals* 8(11).
- Zhu, Jie, Yunjiao Li, Longlong Xue, Yongxiang Chen, Tongxing Lei, Shiyi Deng, and Guolin Cao. 2019. "Enhanced Electrochemical Performance of Li_3PO_4 Modified $\text{Li}[\text{Ni}_{0.8}\text{Co}_{0.1}\text{Mn}_{0.1}]\text{O}_2$ Cathode Material via Lithium-Reactive Coating." *Journal of Alloys and Compounds* 773:112–20. doi: <https://doi.org/10.1016/j.jallcom.2018.09.237>.
- Zhu, Yizhou, Xingfeng He, and Yifei Mo. 2015. "Origin of Outstanding Stability in the Lithium Solid Electrolyte Materials: Insights from Thermodynamic Analyses Based on First-Principles Calculations." *ACS Applied Materials & Interfaces* 7(42):23685–93.